

Inorganic Scintillators for Future HEP Experiments

Chen Hu, Liyuan Zhang and Ren-Yuan Zhu*^a

^a 256-48, HEP, California Institute of Technology, Pasadena, CA 91125, USA

ABSTRACT

Future HEP experiments at the energy and intensity frontiers present stringent challenges to inorganic scintillators in radiation tolerance, ultrafast time response and cost. This paper reports recent progress in radiation hard, ultrafast, and cost-effective inorganic scintillators for future HEP experiments. Examples are LYSO crystals for a precision time of flight detector, LuAG ceramics for an ultracompact, radiation hard shashlik sampling calorimeter, BaF₂:Y crystals for an ultrafast calorimeter, and cost-effective scintillators for a homogeneous hadron calorimeter. Applications for Gigahertz hard X-ray imaging will also be discussed.

INTRODUCTION

Historically, inorganic scintillators are widely used in the high energy physics (HEP) experiments to construct electromagnetic calorimeter, providing the best possible energy resolution and position resolution, good electron and photon identification and reconstruction efficiency. A homogeneous hadron calorimeter (HHCAL) would also provide excellent jet mass resolution by dual readout of either scintillation and Cerenkov light or scintillation light in fast and slow gate. The recent DOE report on HEP detector R&D needs [1] points out the following priority research directions which are related to the inorganic scintillators. Fast and radiation hard inorganic scintillators are needed to face challenges of the unprecedented harsh radiation environment expected by future HEP experiments at the energy frontier, such as the High Luminosity Large Hadron Collider (HL-LHC) and the proposed Future Hadron Circular Collider (FCC-hh), where up to 500 Grad and 5×10^{18} n_{eq}/cm² of one MeV equivalent neutron fluence are expected by the forward calorimeter [2]. Ultrafast inorganic scintillators are needed for future HEP experiments at the intensity frontier to mitigate high event rate and pileup [3]. Cost-effective inorganic scintillators are needed for crystal ECAL and the proposed HHCAL concept. Table 1 lists optical and scintillation properties of fast and ultrafast scintillators.

Table 1 Optical and scintillation properties of fast and ultrafast inorganic scintillators

	BaF ₂	BaF ₂ :Y	ZnO:Ga	YAP:Yb	YAG:Yb	β-Ga ₂ O ₃	LYSO:Ce	LuAG:Ce	YAP:Ce	GAGG:Ce	LuYAP:Ce	YSO:Ce
Density (g/cm ³)	4.89	4.89	5.67	5.35	4.56	5.94	7.4	6.76	5.35	6.5	7.2 ^f	4.44
Melting points (°C)	1280	1280	1975	1870	1940	1725	2050	2060	1870	1850	1930	2070
X ₀ (cm)	2.03	2.03	2.51	2.77	3.53	2.51	1.14	1.45	2.77	1.63	1.37	3.10
R ₉₀ (cm)	3.1	3.1	2.28	2.4	2.76	2.20	2.07	2.15	2.4	2.20	2.01	2.93
λ ₁ (cm)	30.7	30.7	22.2	22.4	25.2	20.9	20.9	20.6	22.4	21.5	19.5	27.8
Z _{eff}	51.6	51.6	27.7	31.9	30	28.1	64.8	60.3	31.9	51.8	58.6	33.3
dE/dX (MeV/cm)	6.52	6.52	8.42	8.05	7.01	8.82	9.55	9.22	8.05	8.96	9.82	6.57
λ _{peak} ^a (nm)	300 220	300 220	380	350	350	380	420	520	370	540	385	420
Refractive Index ^b	1.50	1.50	2.1	1.96	1.87	1.97	1.82	1.84	1.96	1.92	1.94	1.78
Normalized Light Yield ^{a,c}	42 4.8	1.7 4.8	6.6 ^d	0.19 ^d	0.36 ^d	6.5 0.5	100	35* 48*	9 32	115	16 15	80
Total Light yield (ph/MeV)	13,000	2,000	2,000 ^d	57 ^d	110 ^d	2,100	30,000	25,000 ^a	12,000	34,400	10,000	24,000
Decay time ^a (ns)	600 0.5	600 0.5	<1	1.5	4	148 6	40	820 50	191 25	53	1485 36	75
LY in 1 st ns (photons/MeV)	1200	1200	610 ^d	28 ^d	24 ^d	43	740	240	391	640	125	318
LY in 1 st ns/Total LY	9.2%	60%	31%	49%	22%	2.0%	2.5%	1.0%	3.3%	1.9%	1.3%	1.3%
40 keV Att. Leng. (1/e, mm)	0.106	0.106	0.407	0.314	0.439	0.394	0.185	0.251	0.314	0.319	0.214	0.334

^a top/bottom row: slow/fast component; ^b at the emission peak; ^c normalized to LYSO:Ce; ^d excited by alpha particles;

^e ceramic with 0.3 Mg at% co-doping; ^f density for composition Lu_{0.7}Y_{0.3}AlO₃:Ce

Cerium doped lutetium yttrium oxyorthosilicate ($\text{Lu}_{2(1-x)}\text{Y}_{2x}\text{SiO}_5:\text{Ce}$ or LYSO) and lutetium aluminium garnet ($\text{Lu}_3\text{Al}_5\text{O}_{12}$ or LuAG:Ce) show high stopping power, high light output, fast decay time and good radiation hardness against ionization dose and hadrons. LYSO crystals are used to construct a barrel timing layer (BTL) for the CMS upgrade for the HL-LHC, where 5 Mrad ionization dose, 2.5×10^{13} charged hadrons/cm² and 3×10^{14} 1 MeV equivalent neutrons/cm² are expected [4]. They were also proposed for an ultra-compact, radiation hard shashlik calorimeter for the HL-LHC [5]. Yttrium doped barium fluoride crystals ($\text{BaF}_2:\text{Y}$) have an ultrafast scintillation component with 0.5 ns decay time and a suppressed slow component [6]. An ultrafast $\text{BaF}_2:\text{Y}$ total absorption calorimeter is considered by the Mu2e-II experiment [3]. Cost-effective crystals and glasses are under development for the HHCAL concept. It is also interesting to note that ultrafast inorganic scintillators listed in Table 1 may also be used for GHz hard X-ray imaging at future free electron laser facilities [7].

LYSO CRYSTALS AND LUAG CERAMICS

Radiation hardness against ionization dose, protons and neutrons are investigated for LYSO crystal and LuAG ceramic samples from various vendors. The JPL Total Ionization Dose (TID) facility, the CERN PS-IRRAD Proton Facility, and the Weapons Neutron Research facility of the Los Alamos Neutron Science Center (WNR of LANSCE) were used in this investigation. Fig. 1 shows radiation induced absorption coefficient (RIAC) values as a function of integrated ionization dose (Left), proton fluence (Middle), and 1 MeV equivalent neutron fluence (Right), for various LYSO crystal samples, and compared to the radiation hardness specification for CMS BTL LYSO crystals of $3 \times 3 \times 50$ mm³: RIAC < 3 m⁻¹ after 4.8 Mrad, 2.5×10^{13} p/cm² and 3×10^{14} n_{eq}/cm² [4]. In this investigation, we also found that radiation damage induced by protons in LYSO crystals is an order of magnitude larger than that from neutrons. This is due to the ionization energy loss from protons in addition to the damage caused by displacement and nuclear breakup.

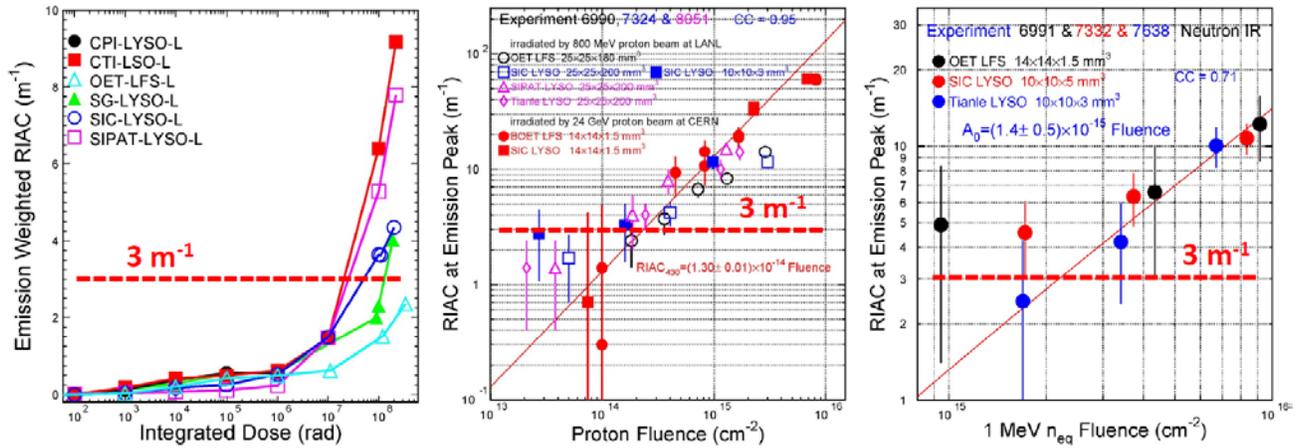


Figure 1. The RIAC values are shown as a function of the ionization dose (Left), proton fluence (Middle), and one MeV equivalent neutron fluence (Right) for LYSO crystals from various vendors.

Fig. 2 show RIAC values as a function of 1 MeV equivalent neutron fluence (Left) and proton fluence (Middle) up to 6.7×10^{15} n_{eq}/cm² and 1.2×10^{15} p/cm² for LuAG:Ce ceramics and LYSO:Ce and BaF₂ crystals. LuAG:Ce ceramics shows a factor of two better radiation hardness than LYSO crystals, so are promising for the FCC-hh [8]. LuAG:Ce ceramics, however, also has slow scintillation component. Fig. 2 (Right) shows that Ca²⁺ co-doping improves the Fast/Total (F/T) ratio, defined as the ratio between the light output in 200 ns and 3,000 ns, to 90%. Investigation continues to improve the F/T ratio and radiation hardness for LuAG:Ce/Ca ceramics.

The left plot of Fig. 3 shows the LuAG:Ce excitation spectrum (red) [8] matches well with the LYSO:Ce emission spectrum (blue) [9], indicating that LuAG:Ce may serve as an effective wavelength shifter for LYSO:Ce crystals. The middle plot shows the proposed RADiCAL concept [10], which uses tungsten plates as absorber, LYSO:Ce crystals as sensitive material and LuAG:Ce ceramic fibers as wavelength shifter. The RADiCAL concept provides an ultra-compact, radiation hard and longitudinally segmented electromagnetic calorimeter for the HL-LHC and FCC-hh. The right plot shows seven $\Phi 1 \times 40$ mm LuAG:Ce ceramic fibers under investigation, which were produced at Shanghai Institute of Ceramics (SIC) by using the laser heated pedestal growth technology for LuAG:Ce fibers.

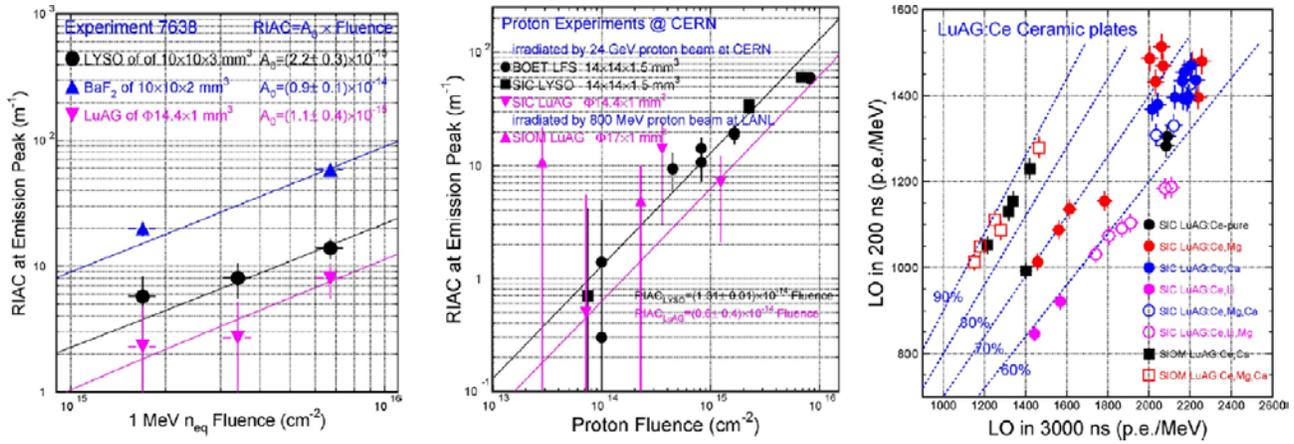


Figure 2. RIAC values are shown as a function of the one MeV equivalent neutron fluence (Left) and proton fluence (Middle) for LuAG:Ce, LYSO:Ce and BaF₂ crystals. Right: The light output in 200 ns and 3 μs gate is shown for LuAG:Ce ceramics.

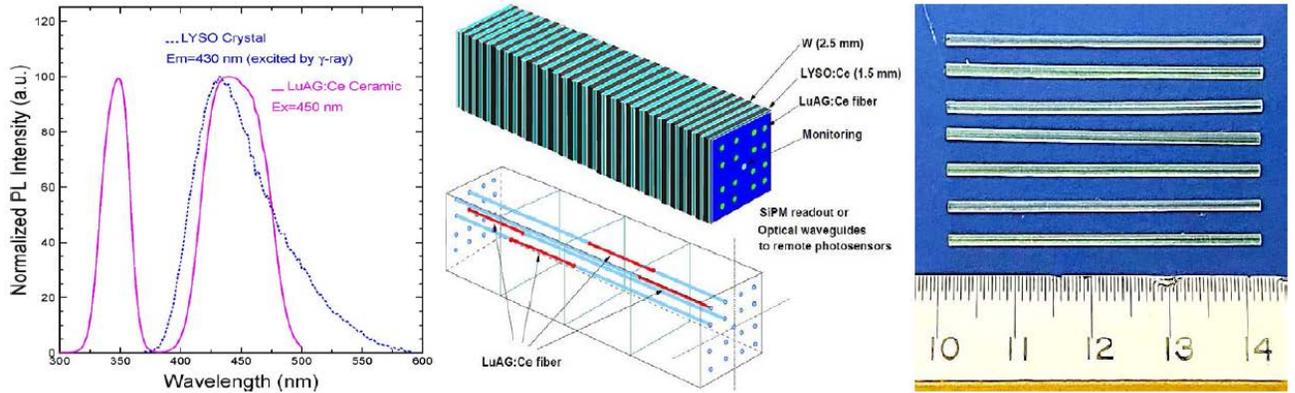


Figure 3. Left: The LuAG:Ce excitation (red) matches well the LYSO:Ce emission (blue). Middle: The RADiCAL concept using radiation hard LYSO:Ce as sensitive material and LuAG:Ce ceramics as wavelength shifter. Right: Seven $\Phi 1 \times 40$ mm LuAG:Ce ceramic fibers produced at SIC by using the laser heated pedestal growth technology.

ULTRAFAST BAF₂:Y CRYSTALS

It is well known that BaF₂ crystals have an ultrafast cross-luminescence scintillation with sub-ns decay time peaked at 220 nm, and a 600 ns slow component peaked at 300 nm with a much higher intensity. The latter causes pileup in a high-rate environment. The left plot of Fig. 4 shows the pulse shape measured by a PMT (top) and a MCP (bottom) for a BaF₂ sample. A decay time of 0.5 ns is observed by the MCP, but not PMT, where 1.4 ns decay time is due to the slow response time of the PMT. It is also known that the slow component in BaF₂ crystals may be suppressed either by rare earth doping in crystals or by using a solar blind photodetector [11]. The middle and right plots of Fig. 4 are respectively the X-ray excited emission spectra and light output as a function of integration time for BaF₂ cylinders of $\Phi 18 \times 21$ mm³ grown at Beijing Glass Research Institute (BGRI) with different Y³⁺ doping levels [6]. They show a reduced slow light intensity for an increased yttrium doping level, while the intensity of the fast emission is maintained.

One of the potential applications of the ultrafast BaF₂:Y scintillation is front imager for GHz hard X-ray imaging required by future free electron laser facilities [12]. Fig. 5 show response of BaF₂, BaF₂:Y, ZnO:Ga and LYSO:Ce crystals to septuplet X-ray bunches with 2.83 ns bunch spacing measured at the advanced photon source facility of ANL. While BaF₂ crystals show clearly separated X-ray bunches with 2,83 ns spacing, the slow crystals do not. In addition, amplitude reduction is also observed for eight septuplets in BaF₂ and LYSO:Ce, which is due to MCP saturation caused by the slow scintillation in BaF₂ and LYSO:Ce, but not in slow-suppressed BaF₂:Y.

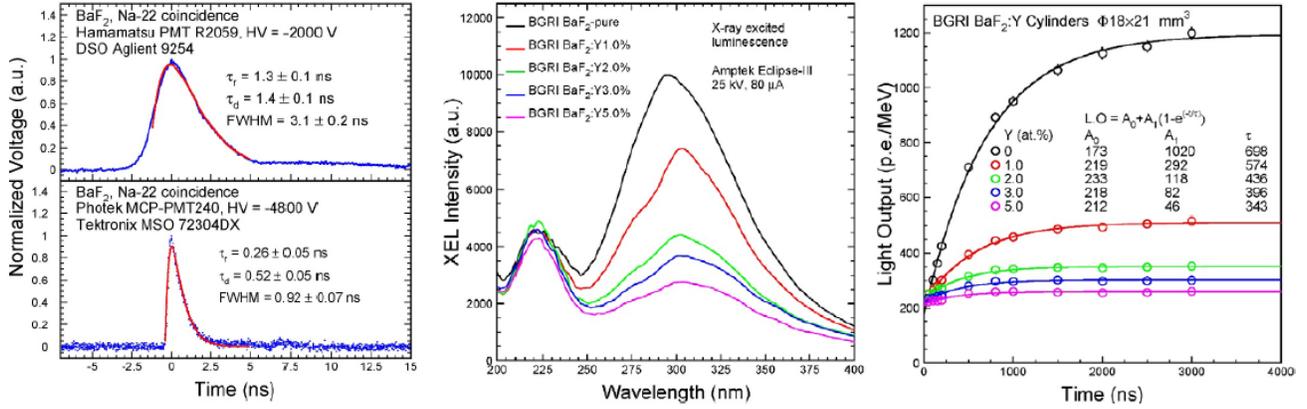


Figure 4. Left: The pulse shape measured by a PMT (top) and a MCP (bottom) shows the ultrafast scintillation light component with 0.5 ns decay time for a BaF₂ sample. The emission (Middle) and integrated light output (Right) are shown for BaF₂ samples with yttrium doping at different levels.

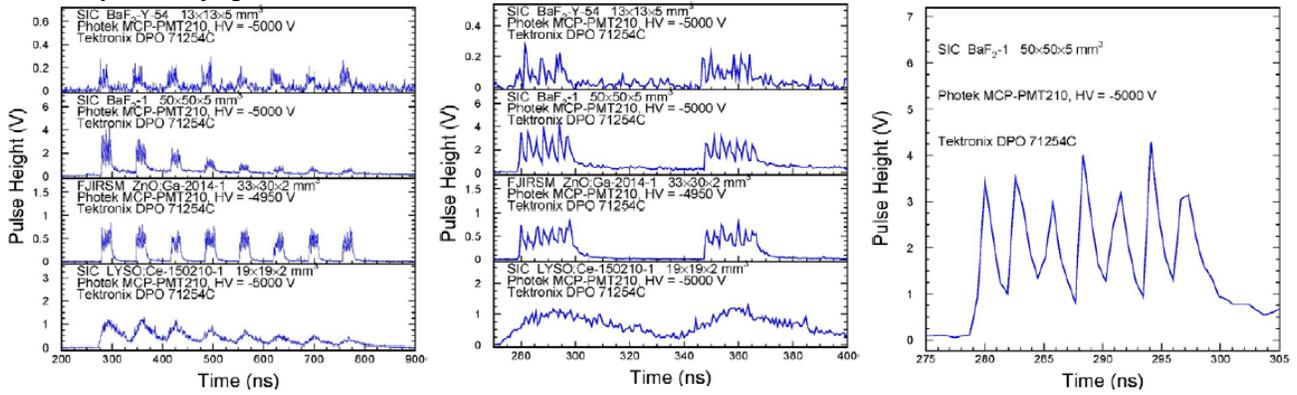


Figure 5. The temporal response to septuplet 30 keV X-ray bunches with 2.83 ns bunch spacing measured at APS of ANL is shown for BaF₂:Y, BaF₂, ZnO:Ga and LYSO:Ce crystal samples.

BaF₂:Y crystals of large size is under development for the Mu2e-II experiment [13]. In addition to yttrium doping in BaF₂ crystals solar-blind photodetectors also improve the F/S ratio, and thus reduce radiation induced readout noise to a level of less than 1 MeV for a BaF₂:Y crystal-based ultrafast calorimeter [13]. Fig. 6 shows the quantum efficiency (QE) of a Photech solar-blind cathode (Left), the particle detection efficiency (PDE) of a FBK solar-blind SiPM (Middle) and the PDE of a Hamamatsu VUV SiPM (Right) as a function of wavelength. The ability of solar-blind photodetectors in slow suppression is clearly demonstrated. R&D continues to develop solar-blind photodetectors [11].

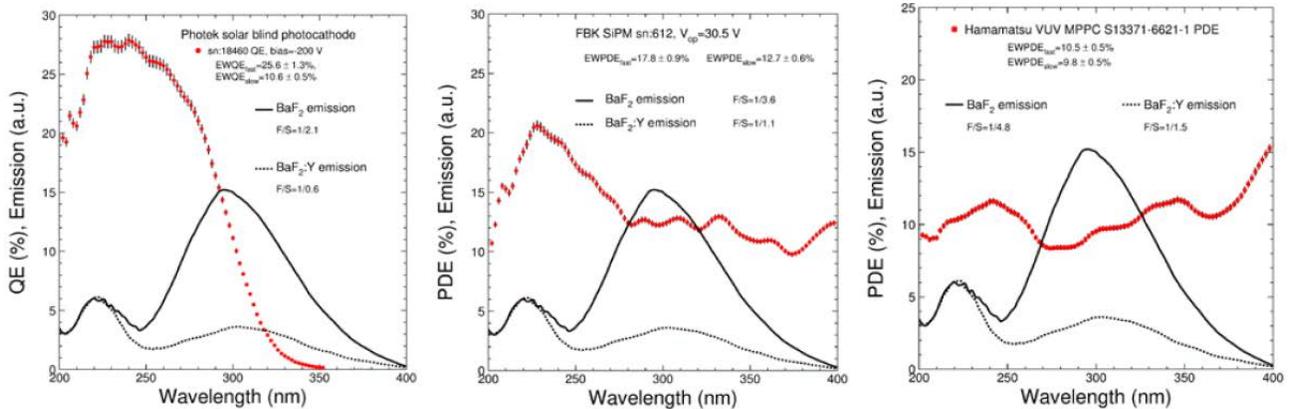


Figure 6. The QE of a Photech solar-blind cathode (Left), the PDE of a FBK solar-blind SiPM (Middle) and the PDE of a Hamamatsu VUV SiPM (Right) are shown as a function of wavelength.

BaF₂:Y crystals of large size is under development for the Mu2e-II experiment. For an ultrafast calorimetry radiation hardness against ionization dose and hadrons is crucial. The left plot of Fig. 7 shows normalized emission weighted transmittance (top) and light output (bottom) as a function of integrated ionization dose up to 130 Mrad for three 20 cm long BaF₂ samples from different vendors. It is interesting to note the ionization dose induced damage saturates around 10 krad until 130 Mrad, indicating limited defect density in these crystals. This is confirmed by normalized light output as a function of proton (Middle) and neutron (Right) fluence up to 9.7×10^{14} p/cm² and 8.3×10^{15} n_{eq}/cm². R&D continues to investigate radiation hardness for large BaF₂:Y crystals [13].

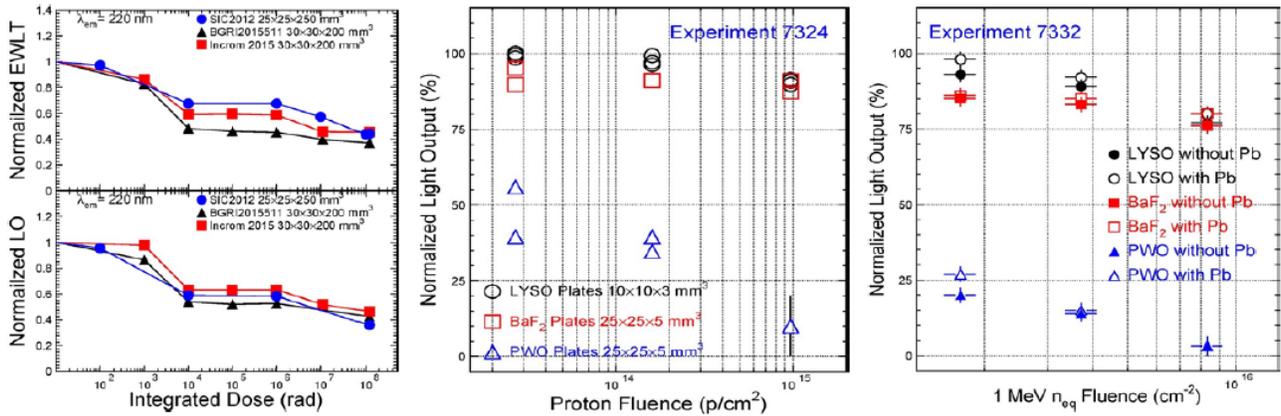


Figure 7. Left: Normalized transmittance (top) and light output (bottom) are shown as a function of integrated ionization dose for three 20 cm long BaF₂ samples from different vendors. Normalized light output is shown as a function of integrated proton (Middle) and one MeV equivalent neutron fluence (Right) for LYSO:Ce, BaF₂ and PWO crystal plates.

COST-EFFECTIVE INORGANIC SCINTILLATORS

An electron-positron Higgs factory is the highest-priority next collider, where good EM and jet resolutions are required for study all decay channels of the Higgs boson. Fig. 8 shows the dual readout CalVision crystal ECAL followed by the IDEA HCAL [15], promising a $3\%/\sqrt{E}$ energy resolution for electrons and photons, and a $27\%/\sqrt{E}$ energy resolution for neutral pions, which is much better than 60% achieved so far by sampling hadron calorimetry.

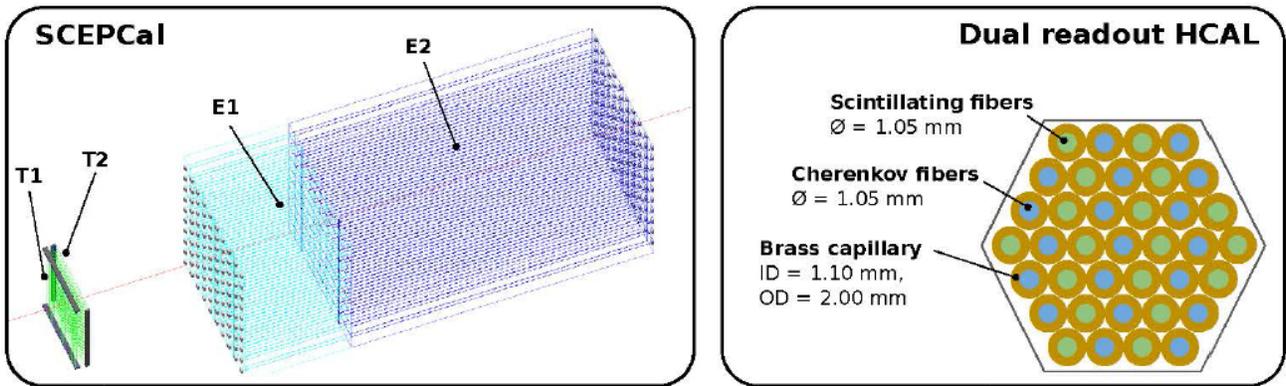


Figure 8. The dual readout CalVision crystal ECAL followed by the IDEA dual readout fiber HCAL.

An even better resolution for hadrons may be achieved by a total absorption hadron calorimeter. Figure 9 (Left) shows a homogeneous hadron calorimeter (HHCAL) concept [16] where a large volume of inorganic scintillators allows event by event corrections with dual readout to recover the missing energies due to nuclei breakup in hadronic jets. Extensive GEANT simulations carried out at Fermilab, ANL and CERN show that a better than $20\%/\sqrt{E}$ energy resolution can be

achieved for charged pions (Middle and Right) by using dual readout of scintillation and Cerenkov light, or scintillation light in short and long gates.

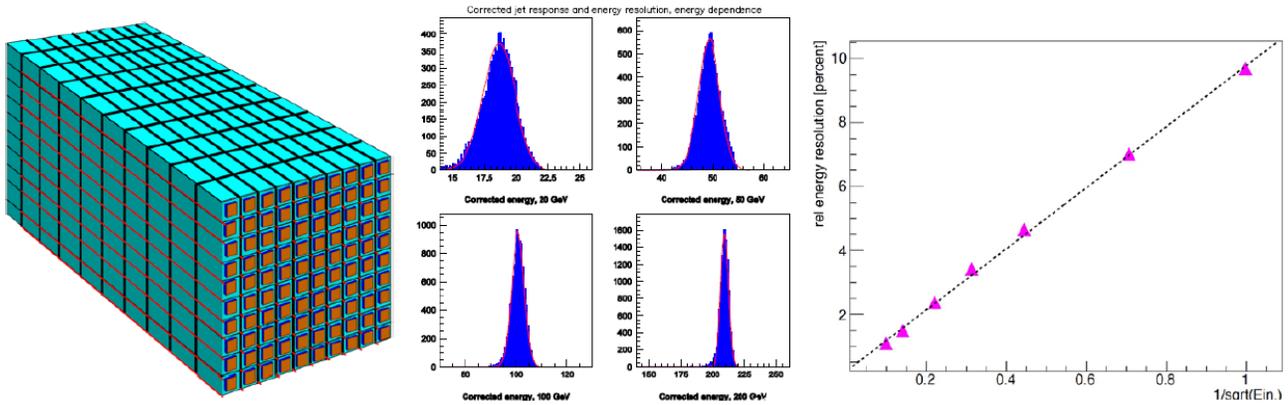


Figure 9. The HHCAL concept (Left) promises a 20%/√E energy resolution for charged pions (Middle) and a better than 20% stochastic term (Right) in hadronic energy resolution.

Because of the large volume of inorganic scintillators required for these total absorption calorimetry, development of cost-effective inorganic scintillators is crucial. The material of choice must be dense, cost-effective, UV transparent (for effective collection of Cerenkov light) and allow for a clear discrimination between the Cerenkov and scintillation light.

Table 2 Optical and scintillation properties of candidate inorganic scintillators for the HHCAL concept

	BGO	BSO	PWO	PbF ₂	PbFCl	Sapphire:Ti	AFO Glass	DSB:Ce Glass ¹	DSB:Ce,Gd Glass ^{2,3}	HFG Glass ⁴
Density (g/cm ³)	7.13	6.8	8.3	7.77	7.11	3.98	4.6	3.8	4.7 - 5.4	5.95
Melting point (°C)	1050	1030	1123	824	608	2040	980 ⁵	1420 ⁶	1420 ⁶	570
X ₀ (cm)	1.12	1.15	0.89	0.94	1.05	7.02	2.96	3.36	2.14	1.74
R _M (cm)	2.23	2.33	2.00	2.18	2.33	2.88	2.89	3.52	2.56	2.45
λ ₁ (cm)	22.7	23.4	20.7	22.4	24.3	24.2	26.4	32.8	24.2	23.2
Z _{eff} value	72.9	75.3	74.5	77.4	75.8	11.2	42.8	44.4	48.7	56.9
dE/dX (MeV/cm)	8.99	8.59	10.1	9.42	8.68	6.75	6.84	5.56	7.68	8.24
Emission Peak ^a (nm)	480	470	425 420	\	420	300 750	365	440 460	440 460	325
Refractive Index ^b	2.15	2.68	2.20	1.82	2.15	1.76	\	\	\	1.50
LY (ph/MeV) ^c	7,500	1,500	130	\	150	7,900	450	3,150	2,500	150
Decay Time ^a (ns)	300	100	30 10	\	3	300 3200	40	180 30	120, 400 50	25 8
d(LY)/dT (%/°C) ^c	-0.9	?	-2.5	\	?	?	?	-0.04	-0.04	-0.37
Cost (\$/cc)	6.0	7.0	7.5	6.0	?	0.6?	?	2.0	2.0?	?

a. Top line: slow component, bottom line: fast component.
 b. At the wavelength of the emission maximum.
 c. At room temperature (20°C).

1. E. Auffray, et al., J. Phys. Conf. Ser. 587, 2015
 2. R. W. Novotny, et al., J. Phys. Conf. Ser. 928, 2017
 3. V. Dornenev, et al., the ATTRACT Final Conference
 4. E. Auffray, et al., NIMA 380 (1996), 524-536
 5. R. A. McCauley et al., Trans. Br. Ceram. Soc., 67, 1968
 6. I. G. Oehlschlegel, Glastech. Ber. 44, 1971

Low density crystals/glasses

Table 2 lists basic optical and scintillation properties of candidate heavy inorganic material for the HHCAL concept, where BGO, BSO, PWO, PbF₂, PbFCl and Sapphire:Ti are crystals, AFO, DSB and HFG are scintillating glasses. The left and middle plots of Fig. 10 show a broad emission peaked at 750 nm with a decay time of 3 μs for two titanium doped Sapphire samples. With Kyropoulos growth technology, the cost of mass-produced Sapphire ingot of Φ50×55 cm is about \$12,000/piece. The right photo of Fig. 10 shows mass-produced sapphire ingots in one production facility. After cutting and polishing, the price of sapphire crystals is expected to be less than \$1/cc, indicating that it is possible to mass-produce inorganic scintillators cost-effectively. While its UV cut-off wavelength of 250 nm and nuclear interaction length of 24 cm are adequate for the HHCAL application, its density and radiation length of 4 g/cc and 7 cm, however,

are not ideal. Work along this line will continue to search for cost-effective heavy inorganic scintillators for these novel calorimeter concepts.

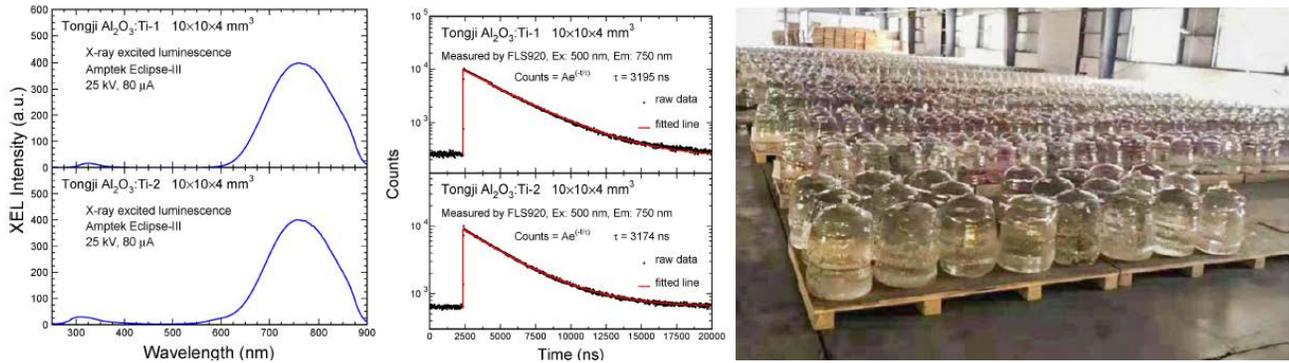


Figure 10. Emission (Left) and decay time (Middle) are shown for two titanium doped Sapphire crystal samples. Right: Sapphire ingots in a production facility.

SUMMARY

Future HEP experiments at the energy frontier require fast and radiation hard calorimetry. The RADiCAL concept utilizes bright and fast LYSO:Ce crystals and LuAG:Ce WLS for an ultra-compact, ultra-radiation hard and longitudinally segmented shashlik calorimeter for HL-LHC and FCC-hh.

Future HEP experiments at the intensity frontier requires ultrafast calorimetry. R&D is on-going to develop large size BaF₂:Y crystals and solar-blind VUV photodetectors for Mu2e-II.

The proposed lepton Higgs factory requires good EM and jet resolutions. The dual readout CalVision crystal ECAL followed by the IDEA HCAL provides an excellent option.

Because of total absorption for hadrons the HHCAL concept promises the best jet mass resolution. Crucial R&D is to develop cost-effective inorganic scintillators of large volume.

Novel inorganic scintillators are needed for all these calorimeter concept.

ACKNOWLEDGEMENTS

This work is supported by the U.S. Department of Energy, Office of High Energy Physics program under Award Number DE-SC0011925.

REFERENCES

- [1] Report of the DOE Office of Science Workshop on “Basic Research Needs Study on HEP Detector Research and Development,” Dec 11-14, 2019, <https://science.osti.gov/hep/Community-Resources/Reports>
- [2] M. Aleksa *et al.*, “Calorimeters for the FCC-hh,” arXiv:1912.09962.
- [3] F. Abusalma, *et al.*, “Expression of Interest for Evolution of the Mu2e Experiment,” arXiv:1802.02599.
- [4] J. Butler *et al.*, “A MIP Timing Detector for the CMS Phase-2 Upgrade,” CERN-LHCC-2019-003, CMS-TDR-020 (2019).
- [5] R.-Y. Zhu, Invited paper “Progress on Inorganic Scintillators for Future HEP Experiments,” doi: 10.1117/12.2596459.
- [6] C. Hu *et al.*, “Development of Yttrium-Doped BaF₂ Crystals for Future HEP Experiments,” IEEE Trans. Nucl. Sci. 66(8), pp. 1854-1860 (2019).
- [7] <https://www.lanl.gov/science-innovation/science-facilities/dmmsc/index.php>

- [8] C. Hu *et al.*, “LuAG ceramic scintillators for future HEP experiments,” Nucl. Instrum. Meth. A 954, pp. 161723 (2020), and “Hadron-Induced Radiation Damage in LuAG:Ce Scintillating Ceramics,” IEEE Trans. Nucl. Sci. 69 (2022) 181-186, DOI 10.1109/TNS.2021.3139050 (2021).
- [9] R. Mao *et al.*, “Emission Spectra of LSO and LYSO Crystals Excited by UV Light, X-Ray and γ -ray,” IEEE Trans. Nucl. Sci. 55(3), pp. 1759-1766 (2008).
- [10] R. Ruchiti *et al.*, “Advanced Optical Instrumentation for Ultra-Compact Radiation Hard Fast-Timing EM Calorimetry,” presented in the CPAD Instrumentation Frontier Workshop 2021 at Stony Brook.
https://indico.fnal.gov/event/46746/contributions/210058/attachments/141115/177602/CPAD_Presentation_3.1_8.21_rr.pdf
- [11] D. Hitlin *et al.*, “Progress on a photosensor for the readout of the fast scintillation light component of BaF₂,” presented in the CPAD Instrumentation Frontier Workshop 2021 at Stony Brook.
https://indico.fnal.gov/event/46746/contributions/210202/attachments/141121/177609/Hitlin_CPAD_210318-.pdf.
- [12] C. Hu *et al.*, “Ultrafast inorganic scintillator-based front imager for Gigahertz Hard X-ray imaging,” Nucl. Instrum. Meth. A 940, pp. 223-229 (2019).
- [13] C. Hu *et al.*, “Development of Novel Inorganic Scintillators for Future High Energy Physics Experiments,” Presented in the CPAD Instrumentation Frontier Workshop 2021 at Stony Brook.
https://indico.fnal.gov/event/46746/contributions/210069/attachments/141179/177687/Chen_CPAD_2021.pdf.
- [14] L. Zhang *et al.*, “QE/PDE of VUV Photodetectors for BaF₂ Readout,” will be published in IEEE Trans. Nucl. Sci. (2022), doi: 0.1109/TNS.2022.3149840.
- [15] J. Qian *et al.*, “A Dual Readout Calorimeter with a Crystal ECAL,” presented in the CPAD Instrumentation Frontier Workshop 2021 at Stony Brook.
https://indico.fnal.gov/event/46746/contributions/210056/attachments/141113/177599/CPAD_CalVision.pdf
- [16] M. Demateau *et al.*, “Homogeneous Hadron Calorimetry for a Future Higgs Factory,” presented in the CPAD Instrumentation Frontier Workshop 2021 at Stony Brook.
https://indico.fnal.gov/event/46746/contributions/210064/attachments/141214/177758/Demarteau_cpad-hhcal.pdf