

Experimental investigation of the asymmetric spectroscopic characteristics of electron- and hole-doped cuprates

N.-C. Yeh,^{a*} C.-T. Chen,^a A. D. Beyer,^a C. R. Hughes,^a T. A. Corcovilos,^a S. I. Lee^b

^a*Department of Physics, California Institute of Technology, Pasadena, CA 91125, USA*

^b*Department of Physics, Pohang University of Science and Technology, Pohang, Korea*

Abstract

Quasiparticle tunneling spectroscopic studies of electron- (n-type) and hole-doped (p-type) cuprates reveal that the pairing symmetry, pseudogap phenomenon and spatial homogeneity of the superconducting order parameter are all non-universal. We compare our studies of p-type $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ and n-type infinite-layer $\text{Sr}_{0.9}\text{Ln}_{0.1}\text{CuO}_2$ ($\text{Ln} = \text{La}, \text{Gd}$) systems with results from p-type $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_x$ and n-type one-layer $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_4$ cuprates, and attribute various non-universal behavior to different competing orders in p-type and n-type cuprates.

Keywords: Quasiparticle spectra; pseudogap; pairing symmetry; competing orders

1. Introduction


The presence of competing orders in the ground state of cuprate superconductors [1] results in rich phenomena and complications for unraveling the pairing mechanism. Recent experimental development [1-3] reveals significant non-universal phenomena and asymmetric characteristics between n-type and p-type cuprates as the consequences of competing orders. In particular, the asymmetric characteristics among n-type and p-type cuprates may be attributed to the differences in their low-energy spin excitations [1,2]. We suggest that the *incommensurate* spin excitations associated with charge modulations in *p-type* cuprates may result in a charge nematic (CN) phase that competes with superconductivity (SC), yielding pseudogap phenomena and nano-scale phase separations in two-dimensional (2D) cuprates and long-range SC order in 3D cuprates [1,2]. In contrast, *commensurate* spin excitations in *n-type* cuprates, as manifested by neutron scattering [4] and implied by quasiparticle spectra [2,3], are indicative of the coexistence of antiferromagnetism (AFM) with SC.

2. Competing orders and pseudogap in p-type cuprates

The doping of holes into the CuO_2 planes of cuprates is known to induce gapped spin excitations in the CuO_2 plane. One of the possible ground states of the hole-doped CuO_2 plane is the stripe phase which accommodates gapped spin excitations via charge modulations [1]. However, a charge stripe phase with long-range order is energetically very costly. A compromised competing ground state phase in the presence of disorder could be a CN phase that involves local charge modulations while evading strong Coulomb repulsion. In general, the competition between two order parameters can result in three possible phase diagrams as a function of the chemical potential [1-3]: 1) nano-scale phase separations of the two phases, 2) coexistence of the two phases, and 3) disorder intermediate between the two phases. For highly 2D p-type cuprates such as $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_x$ (Bi-2212), the resulting ground state could reflect either Case 1) or Case 2), because SC involving continuous U(1) symmetry breaking cannot sustain long-range homogeneity in 2D [2], and also because the CN phase could be better stabilized by local disorder in 2D [8].

* Corresponding author. Tel.: +1-626-395-4313; fax: +1-626-683-9060; e-mail: ncyeh@caltech.edu. Research at Caltech is supported by NSF.

The CN phase may extend above T_c and yield the pseudogap (PG) phenomenon. In contrast, highly 3D p-type cuprates like $\text{YBa}_2\text{Cu}_2\text{O}_{7-\delta}$ (YBCO) may belong to Case 2), with homogeneous SC manifested by scanning tunneling spectroscopy [1], NMR [5] and microwave [1] studies. Figure 1 compares the spatial evolution of quasiparticle

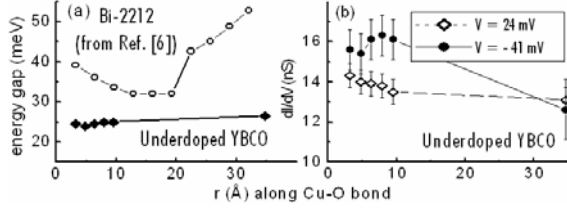

spectral characteristics between YBCO and Bi-2212. Fig.1 Spatial evolution of quasiparticle spectral features along the Cu-O bonding direction: (a) energy gap of underdoped YBCO ($T_c \approx 60$ K) [1] and Bi-2212 ($T_c \approx 79$ K) [6]; (b) differential conductance (dI/dV) of underdoped YBCO at bias voltages $V = 24$ mV and -41 mV.

To investigate the possibility of locally pinned CN coexisting with SC in Bi-2212, we consider the effects of three sources of elastic scattering on the energy (E) and momentum transfer (q) dependence of the tunneling conductance $AG(q, E)$, which is proportional to the Fourier-transformed local density of states (FT-LDOS) $\rho_q(E)$ [7,8]: point defects in the SC region, stripes in the pinned CN region, and 1D “edge states” separating the CN and SC regions. Assuming weak scattering potentials and using the first-order T-matrix approximation [8], we find that $\rho_q(E) \propto \int d^3k \delta(E-E_k) \delta(E-E_{k+q}) |V(\mathbf{q})| F_{\pm}(k, \mathbf{q})$, where $|V(\mathbf{q})|$ is the elastic scattering matrix in the Born approximation, and $F_{\pm}(k, \mathbf{q})$ are the coherence factors for spin-independent (+) and spin-dependent (-) interactions [8]. Examples of the quasiparticle FT-LDOS are shown in Figs. 2(a)-(c), where we have included 24 randomly distributed defects in an area of $(200a_0 \times 200a_0)$. We note that the FT-LDOS in Fig. 2(b) due to CN scattering of quasiparticles reveals more intense features along the $(\pi, 0)/(0, \pi)$ directions than those due to point and edge defects in Figs. 2(a) and 2(c). The combined spectra of both point- and 1D-scattering centers seem to agree better with experimental observation [7,8], implying that pinned CN could coexist with SC in Bi-2212.

3. Coexisting AFM and SC in n-type cuprates

The presence of commensurate spin excitations in one-layer n-type cuprates, as revealed from neutron scattering data [4], is consistent with the coexistence of a long-range AFM order parameter in the SC state, and the absence of charge modulations may account for the absence of PG above T_c [9]. Further evidence for coexisting AFM and SC is provided by our quasiparticle spectra of the n-type

infinite-layer cuprate $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$: For small tunneling currents (< 20 nA), similar spectral characteristics with $\Delta_{SC} = 13$ meV prevail, whereas for large tunneling currents (> 80 nA), a different large-gap spectrum ($\Delta_{AFM} \sim 25$ meV) emerges. The field-induced pseudogap below T_c and above the upper critical field $B_{c2}(T)$ for one-layer n-type cuprates [9] is also suggestive of remnant AFM or a spin-flop (SF) phase upon the suppression of SC at $B > B_{c2}(T)$. In Fig. 3 we compare the phase diagram of the n-type infinite-layer (from our magnetization measurements) with that of the one-layer cuprates [9]. The different vortex phase boundaries of $\text{Sr}_{0.9}\text{Gd}_{0.1}\text{CuO}_2$ and $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$ suggest excess pinning effects due to the magnetic moments of Gd.

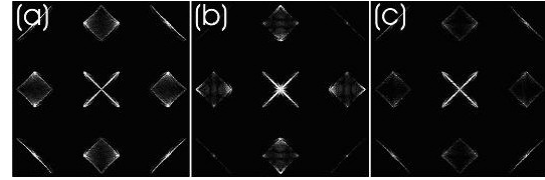


Fig.2 Quasiparticle FT-LDOS associated with (a) non-magnetic point defects, (b) stripes in CN, and (c) edge states for $(q_x, q_y) = (\pm\pi/a_0, \pm\pi/a_0)$, $\Delta_d = 40$ meV and $E = 20$ meV. The sharper contrast represents stronger interference intensity.

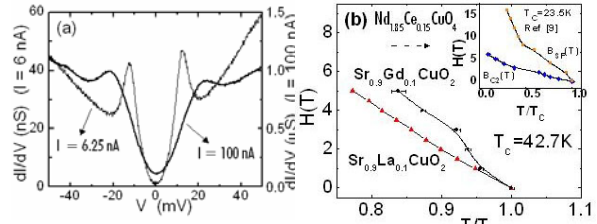


Fig.3 (a) Quasiparticle tunneling spectra of $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$ at 4.2 K taken with tunneling currents of $I = 6.25$ nA and 100 nA. (b) Magnetic phase diagram of n-type cuprates: infinite-layer (main panel) and one-layer (inset). In the inset $B_{SF}(T)$ refers to a spin-flop phase for $H \parallel c$ -axis.

References

- [1] N.-C. Yeh, Bulletin of Assoc. Asia Pacific Phys. Soc. Vol. 12, No. 2 (2002) 2 [cond-mat/0210656].
- [2] N.-C. Yeh and C.-T. Chen, Int. J. Mod. Phys. B 17 (2003) 3575 [cond-mat/0302217].
- [3] C.-T. Chen et al., Phys. Rev. Lett. 88 (2002) 227002.
- [4] M. Matsuda et al., Phys. Rev. B 66 (2002) 172509.
- [5] J. Bobroff et al., Phys. Rev. Lett. 89 (2002) 157002.
- [6] K. M. Lang et al. Nature 415 (2002) 412.
- [7] J. E. Hoffman et al., Science 297 (2002) 1148.
- [8] C.-T. Chen and N.-C. Yeh, Phys. Rev. B 68 (2003) 220505(R) [cond-mat/0307660].
- [9] S. Kleefisch et al., Phys. Rev. B 63 (2001) 100507.